

Investigation of Vacancy Diffusion in Crystalline LIPON Compounds by Means of Density Functional Theory

Project Manager
Pascal Henkel

Principal Investigator
Prof. Dr. Doreen Mollenhauer

Project Term
2019 - 2019


Project Areas
Physical and Theoretical Chemistry

Clusters
Yacana Hochleistungsrechner
Gießen, FUCHS-CSC Frankfurt

Software
VASP

Institute
Institute of Physical Chemistry

University
Justus Liebig University Giessen

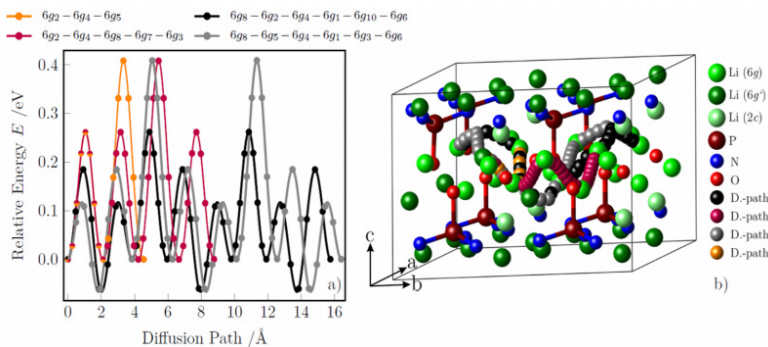

Introduction

Due to an ever-increasing energy demand worldwide, new and efficient energy storage systems are needed more and more. Lithium-ion batteries have emerged as a promising storage medium and therefore have been the subject of intensive research for decades. The performance of such batteries is significantly dependent on the electrode-electrolyte interaction [1]. In this context, Lithium Phosphorus Oxynitride (LIPON) has proven to be a solid state electrolyte of great interest [2]. LIPON compounds have the stoichiometry $\text{Li}_x\text{PO}_y\text{N}_z$ with $x = 2y + 3z - y$. Due to the different $\text{PO}_u\text{N}_{4-u}$ (with $u = 1-4$) building blocks a variety of n dimensional structures are possible [3-5]. For a better understanding of the influence of these n dimensional anionic building blocks on defect formation energies and lithium diffusion, we have investigated two crystalline structures [3,4].

Methods

To determine the diffusion barriers and the defect formation energies of lithium vacancies of LIPON bulk phases, we applied density functional theory using VASP [5]. We not only investigated the diffusion barriers, but also the influence of different functionals and dispersion corrections.

Results

We are presenting our density functional theory results for two selected crystalline LIPON structures. The first LIPON structure (see Fig. 1, 0D structure) consists of three energetically non-equivalent lithium positions, with the 6g Wyckoff position being the most energetically favourable (green), followed by the 2c-position (light green) with a relative energy of 0.30 eV and finally the 6g' position (dark green) with a relative energy of 0.82 eV.

This structure is composed of PON_3 acid building blocks. The deviating energies of the 6g and 6g' positions are due to the fact that the 6g' position is located near the three nitrogen atoms, whereas the 6g position is located at the O-tip of the PON_3 tetrahedron. This means that vacancy diffusion processes can take place both in the ab-plane (on all three Wyckoff positions) and in c-direction between the Wyckoff positions. The diffusion within the 6g position is - with 0.27 eV - the energetically most favourable. In addition, it is demonstrated that the diffusion from a 6g' to a 6g position with a barrier of 0.01 eV is significantly more energetically favourable than the diffusion within the 6g' position (within the plane: 0.41 eV). The analogue is observed for the 2c position (within the plane: larger than 1.8 eV and from 2c to 6g: 0.04 eV). Therefore we have shown for this 0D LIPON structure that the vacancy diffusion takes place exclusively within the 6g position, whereas a diffusion along the c-axis from the 6g position is energetically not to be expected. In the second LIPON structure (see Fig. 2, 0D structure) the lithium ions exclusively occupy the 8b-Wyckoff position. This structure is composed of $\text{PO}_2\text{N}_2^{2-}$ chain-linked building blocks. In this structure the vacancy diffusion is not determined by the Wyckoff positions, but by the orientation to the $\text{PO}_2\text{N}_2^{2-}$ chains. It is shown that the diffusion perpendicular and vertical to the chains is energetically equal (with 0.62 eV). However, the diffusion parallel to the chain alignment (see Fig. 2 orange curve) with 0.41 eV is energetically the most favourable and so the preferred one. This diffusion takes place parallel to two stacked $\text{PO}_2\text{N}_2^{2-}$ chains, whereas the diffusion parallel to one chain (see Fig. 2 black curve) is energetically unfavourable (larger than 1.6 meV)[6]. As shown, the microscopic structure and orientation of the anionic building blocks have a considerable influence for the diffusion. A comparison of 11 different functionals (with and without dispersion corrections and van-der Waals functionals) demonstrates that the choice of a suitable functional is important. Also, overall the functionals provide similar same results, differences can be observed on examining the different diffusion paths in a qualitative and quantitative manner (see Fig. 3 for LIPON with isolated tetrahedrons) [7].

Outlook

Our investigations have shown that the structure of $\text{PO}_u\text{N}_{4-u}$ building blocks has a significant influence on the diffusion of vacancies within the LIPON bulk phase. In the next step we will extend the vacancy diffusion to a pseudo-crystalline bulk phase to further increase the dimension of $\text{PO}_u\text{N}_{4-u}$ building blocks [8]. Subsequently the interstitial diffusion within those three LIPON structures will be investigated in order to gain further insights into the diffusion mechanisms occurring in LIPON. Our aim is to understand the diffusion processes sufficiently to generate an amorphous-like structure using evolutionary algorithms.

Figures

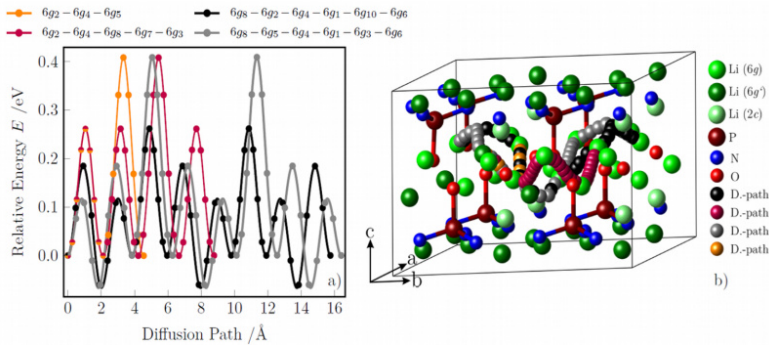


Figure 1: Diffusion path of lithium vacancy diffusion at the 6g Wyckoff position for the LIPON structure with isolated PON_3^{6-} tetrahedrone. (0D-LIPON) a) energetic and b) graphical representation of the different diffusion paths [6].

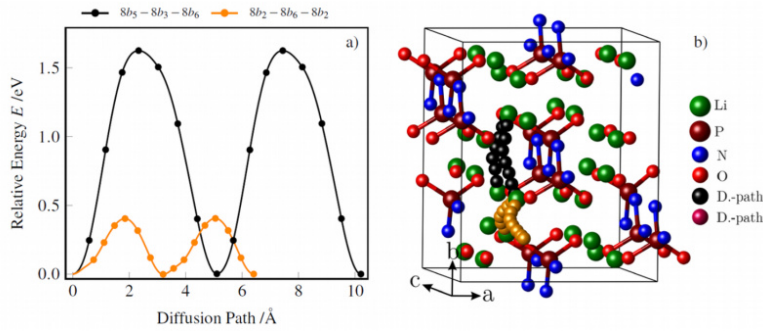


Figure 2: Diffusion path of the lithium vacancy diffusion along the c-axis for the LIPON structure with chain-linked $\text{PO}_2\text{N}_2^{2-}$ tetrahedrone. (1D-LIPON) a) energetic and b) graphical representation of the different diffusion paths [6].

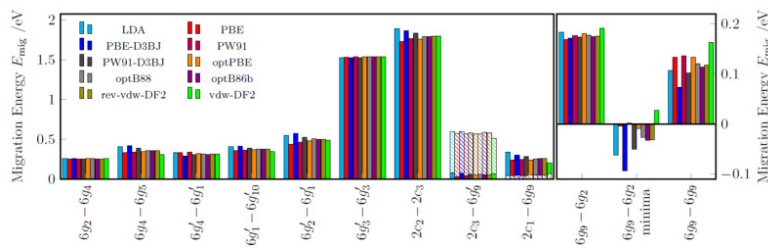


Figure 3: Influence of 11 different exchange-correlation-functionals on the diffusion barriers in LIPON (isolated PON_3 tetrahedrone structure). Forth (full filled) and back diffusion (stiffened filled) differ for the two pathways $2c_3$ - $6g_9$ and $2c_1$ - $6g_9$ [7].

Reference

- [1] Takada, Kazunori: Progress and prospective of solid-state lithium batteries; Acta Materialia 61, 759-770 (2013).
<https://doi.org/10.1016/j.actamat.2012.10.034>
- [2] Bates, J.B.; Dudney, N.J.; Gruzalski, G.R.; Zuhr, R.A.; Choudhury, A.; Luck, C.F.; Robertson, J.D.: Electrical properties of amorphous lithium electrolyte thin films; Solid State Ion., 53-56, 647-654 (1992).
[https://doi.org/10.1016/0167-2738\(92\)90442-R](https://doi.org/10.1016/0167-2738(92)90442-R)
- [3] Al-Qawasmeh, Ahmad; Holzwarth, N.A.W.: Li₁₄P₂O₃N₆ and Li₇PN₄: Computational study of two nitrogen rich crystalline LiPON electrolyte materials; J. Power Sources 364, 410-419 (2017).
<https://doi.org/10.1016/j.jpowsour.2017.08.025>
- [4] Senevirathne, Keerthi; Day, Cynthia S.; Gross, Michael D.; Lachgar, Abdessadek; Holzwarth, N.A.W.: A new crystalline LiPON electrolyte: Synthesis, properties, and electronic structure; Solid State Ion. 233, 95-101 (2013). <https://doi.org/10.1016/j.ssi.2012.12.013>
- [5] Kresse, G.; Furthmüller, J.: Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set; Phys. Rev. B, 54, 11169-11186 (1996). <https://doi.org/10.1103/PhysRevB.54.11169>
- [6] P.Henkel, D. Mollenhauer, Manuscript in preparation.
- [7] P.Henkel, D. Mollenhauer, Manuscript in preparation.
- [8] Sicolo, Sabrina; Albe, Karsten: First-principles calculations on structure and properties of amorphous Li₅P₄O₈N₃ (LiPON); J. Power Sources 331, 382-390 (2016).
<https://doi.org/10.1016/j.jpowsour.2016.09.059>

Last Update: 2022-06-14 17:54