

# Calculations of Vibrational Spectra for Different Facets of Ceria Using Density Functional Theory (DFT)

Project Manager  
Marc Ziemba

Researchers  
Dr. M. Verónica Ganduglia-Pirovano  
and Dr. Christian Schilling


Principal Investigator  
Prof. Dr. Christian Hess

Project Term  
2019 - 2020

Clusters  
Lichtenberg Cluster Darmstadt

Software  
VASP

University  
Technische Universität Darmstadt

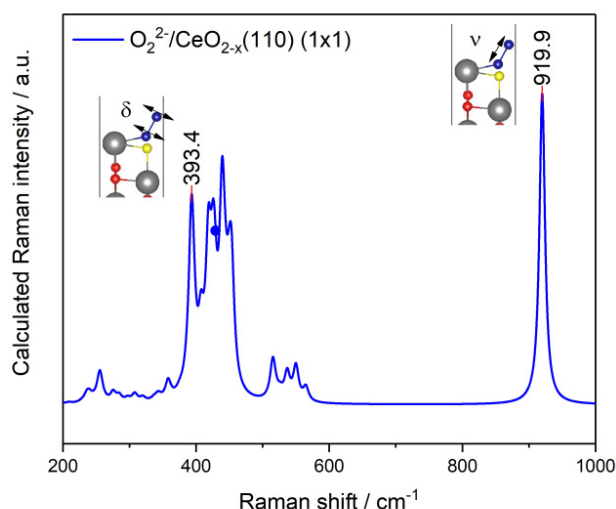

## Introduction

Ceria is an important support material for precious metals to catalyze oxidation reactions such as CO oxidation or the water gas shift reaction. Despite its widespread use, the role of ceria in the catalysts' function, especially the influence of the ceria surface termination, is not well understood and is the subject of current research. Therefore, a combination of density functional theory (DFT) and Raman spectroscopy will be used to enable interpretations at the molecular level. Within this combination of theory and experiment it is possible to gain new insight into reaction mechanisms and the influence of the surface termination.

## Methods

The general procedure is to perform a structure relaxation with tight convergence criteria within DFT+U framework. Then, a vibrational analysis is performed, where normal modes are calculated employing a method based on density functional perturbation theory (DFPT), followed by the calculation of IR and/or Raman activities. The calculation of Raman intensities is computationally demanding due to the fact that it depends on the third order derivative of the energy. These calculations, i.e., the simulations of the Raman and IR spectra, run in close interaction with the corresponding

experiments to provide a direct interpretation of the experimental results.

## Results

In previous project periods, the most stable  $\text{CeO}_2(111)$  and its interaction with small molecules from the gas phase was examined in great detail. In this project period, the goal was to understand the influence of the surface termination on the catalytic behavior. The  $\text{CeO}_2(100)$  and  $\text{CeO}_2(110)$  terminations are accessible by hydrothermal synthesis and can be modeled in theory. For the catalytic experiments the samples were loaded with gold and the gold structures were also studied theoretically. First, we took a closer look at the oxygen activation, which is particularly interesting for reactions where lattice oxygen is needed, e.g. the water-gas shift reaction or the CO oxidation. Regarding the oxygen activation we can observe a strongly surface facet dependent behavior. Overall, we find facilitated peroxide formation at the  $\text{CeO}_2(100)$  surface leading to distinct Raman signals. This is in line with the DFT calculations that predict the formation of a surface oxygen vacancy followed by peroxide formation as a net exothermic process at the  $\text{CeO}_2(100)$  surface, but not at the more stable facets, namely,  $\text{CeO}_2(110)$  and  $\text{CeO}_2(111)$ . As one of the surface peroxide features, we observe a Raman band at  $354\text{ cm}^{-1}$ , the symmetry of which had not been resolved yet in the literature. In combination with DFT calculations we readily can assign this band to a deformation vibration of surface peroxides (see Figure 1). Furthermore, DFT calculations show that the interaction of gold with ceria depends on the surface facets and that gold lowers the defect formation energy, which is in line with our experimental results obtained during CO oxidation. Moreover, we detect an adsorbate band at  $1647\text{ cm}^{-1}$  for the rods, which contain both the  $\text{CeO}_2(110)$  and  $\text{CeO}_2(111)$  facet. Using the combination of theory and experiment this band can be assigned to carbonate species, which are formed at lower temperatures ( $60\text{ }^\circ\text{C}$ ); remarkably, and these carbonate species may block active sites, because of the strong adsorption energies on  $\text{CeO}_2(100)$  and  $\text{CeO}_2(110)$ , and are therefore of relevance for catalysis. To elucidate the mechanism of the water gas shift reaction we performed isotopic exchange experiments. In this context a strong red-shift of the  $F_{2g}$  band, which is an indicator for lattice oxygen, is observed. This leads to the question how complete the exchange of lattice oxygen is. To answer this question, the shifts of the  $F_{2g}$  band for a complete substitution of  $^{16}\text{O}$  by  $^{18}\text{O}$  were calculated using DFT calculations (for spectra of  $\text{Ce}^{18}\text{O}_2$  and  $\text{Ce}^{16}\text{O}_2$  see Figure 2), indicating a red-shift of  $23\text{ cm}^{-1}$ . Interestingly during the water-gas shift reaction a band at  $1079\text{ cm}^{-1}$  is detected for the rods, which has not been discussed in literature. Using DFT this band can be assigned to superoxides adsorbed on a  $\text{CeO}_2(110)$  facet, which occurs at significantly lower wavenumber than on  $\text{CeO}_2(111)$  or  $\text{CeO}_2(100)$  facets. Furthermore, the exclusive occurrence of the  $1079\text{ cm}^{-1}$  band under reaction conditions is in line with our DFT calculations, which show that superoxide adsorption is facilitated on a reduced surface. Thus, based on our experimental and theoretical findings, we can attribute the Raman band at  $1079$

$\text{cm}^{-1}$  to superoxide adsorbed on a reduced  $\text{CeO}_2(110)$  surface. Summarizing, our results show the potential of a combined operando Raman and DFT approach to characterize e.g. adsorbates at the low index surfaces of ceria, which is of importance for a detailed understanding of the activity behavior of ceria-based catalysts.

## Discussion

The combination of DFT calculations and vibrational spectroscopy enables a detailed view of the reaction process. However, the obtained results are only as good as the theoretical model that is used for the calculated structures. For example, regarding the polar  $\text{CeO}_2(100)$  surface it has to be considered that purely Ce- and O-terminating areas may also be present. Furthermore, it is difficult to predict the exact structure of the gold clusters on the surface, since the clusters are very small and difficult to see with imaging methods such as HR-TEM due to the contrast to cerium. For this reason, we calculate several smaller gold clusters in order to determine their influence. Finally, it should be mentioned that the calculations are done within the PBE+U framework, which is a reasonable approximation in terms of vibrational modes. This is, however, different for electronic structures, for which the use of hybrid functionals (HSE06) is essential. Regarding the electronic structures, it is a future goal to be able to better understand the results from operando UV-Vis measurements with the help of theoretically calculated absorption spectra, which is a research area, which has great potential but has barely been touched in the literature.

## Figures

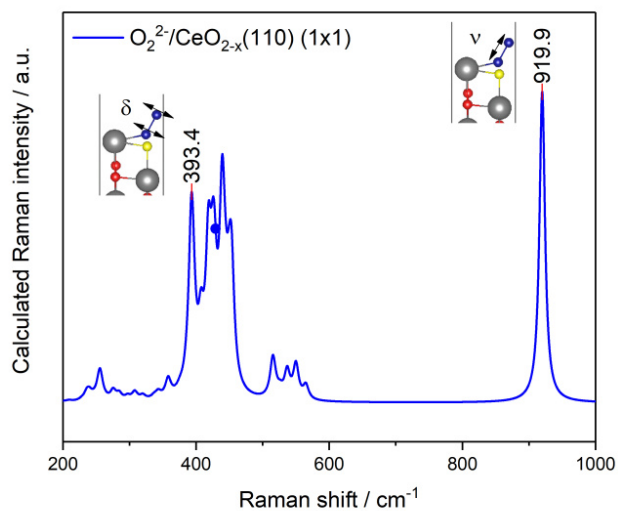


Figure 1: Calculated Raman spectrum for  $\text{O}_2^{2-}/\text{CeO}_{2-x}(110)$  with  $(1 \times 1)$  periodicity. The band positions of the peroxide vibrations are indicated together with the corresponding symmetry.

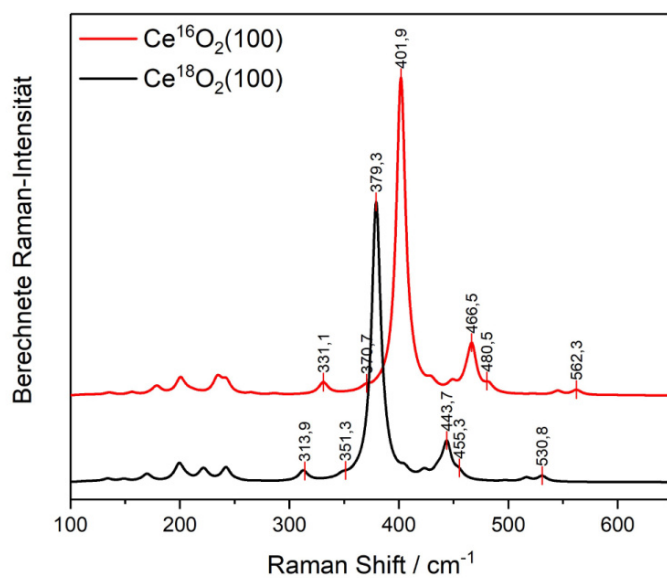


Figure 2: Calculated Raman spectra for  $\text{CeO}_2(100)$  with  $c(1 \times 1)$  periodicity. The spectrum for  $\text{Ce}^{16}\text{O}_2$  is shown in red and that for  $\text{Ce}^{18}\text{O}_2$  in black. The positions of the surface modes and the  $F_{2g}$  band are indicated.

## Publications

Schilling, C.; Ziemba, M.; Ganduglia-Pirovano, M. V.; Hess, C.: Identification of Single-Atom Active Sites in CO Oxidation Over Oxide-Supported Au Catalysts. *J. Catal.*, 2020  
<https://doi.org/10.1016/j.jcat.2020.01.022>

Ziemba, M.; Ganduglia-Pirovano, M. V.; Hess, C.: Insight into the mechanism of the water-gas shift reaction over Au/CeO<sub>2</sub> catalysts using combined operando spectroscopies. *Faraday Discuss.*, 2020  
<https://doi.org/10.1039/C9FD00133F>

Ziemba, M.; Ganduglia-Pirovano, M. V.; Hess, C.: Elucidating the Oxygen Storage-Release Dynamics in Ceria Nanorods by Combined Multi-Wavelength Raman Spectroscopy and DFT. *J. Phys. Chem. Lett.* 2020, 8554–8559. <https://doi.org/10.1021/acs.jpcclett.0c02607>

Ziemba, M.; Hess, C.: Influence of Gold on the Reactivity Behaviour of Ceria Nanorods in CO Oxidation: Combining Operando Spectroscopies and DFT Calculations. *Catal. Sci. Technol.* 2020, 10 (11), 3720–3730.  
<https://doi.org/10.1039/D0CY00392A>

## Reference

Schilling, C.; Hess, C.: Elucidating the Role of Support Oxygen in the Water-Gas Shift Reaction over Ceria-Supported Gold Catalysts Using Operando Spectroscopy. *ACS Catal.*, 2019, 9, 1159–1171.  
<https://doi.org/10.1021/acscatal.8b04536>

Schilling, C.; Ganduglia-Pirovano, M. V.; Hess, C.: Experimental and Theoretical Study on the Nature of Adsorbed Oxygen Species on Shaped Ceria Nanoparticles, *J. Phys. Chem. Lett.*, 2018, 9, 6593–6598.  
<https://doi.org/10.1021/acs.jpcclett.8b02728>

Schilling, C.; Hess, C.: Real-Time Observation of the Defect Dynamics in Working Au/CeO<sub>2</sub> Catalysts by Combined Operando Raman/UV-Vis Spectroscopy. *J. Phys. Chem. C*, 2018, 122(5), 2909–2917.  
<https://doi.org/10.1021/acs.jpcc.8b00027>

Schilling, C.; Hofmann, A.; Hess, C.; Ganduglia-Pirovano, M. V.: Raman Spectra of Poly-crystalline CeO<sub>2</sub>: A Density Functional Theory Study, *J. Phys. Chem. C*, 2017, 121(38), 20834–20849.  
<https://doi.org/10.1021/acs.jpcc.7b06643>

*Last Update:* 2022-04-24 12:41