

# Investigation of the Cell Size Effect of $\text{CeO}_2$ on the Calculated Raman Spectra of $\text{VO}_x/\text{CeO}_2$ Catalysts


Project Manager  
Simone Rogg

Principal Investigator  
Prof. Dr. Christian Hess

Project Term  
2019 - 2019

Software  
VASP

University  
Technische Universität Darmstadt

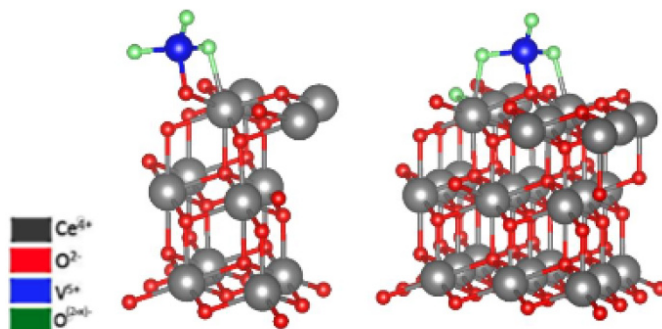

## Introduction

Ceria ( $\text{CeO}_2$ ) is an important support material for transition metal based oxides like vanadia ( $\text{VO}_x$ ). These  $\text{VO}_x/\text{CeO}_2$  catalysts are used in oxidation reactions like the partial oxidation of different alcohols and alkanes. [1] The ODH of propane is a reaction of great potential for industrial applications to synthesize propylene directly from propane as an alternative to steamcracking, for example. The process is not used on a large scale yet, since the reaction leads to low yields due to the combustion of propane to  $\text{CO}_2$ . [2] This might be overcome by the catalytic oxidation using  $\text{VO}_x/\text{CeO}_2$ . To optimize the catalyst, the knowledge of the reaction mechanism for the ODH of propane over ceria supported vanadia catalysts is of great importance. To investigate the mechanism a combined approach of operando Raman spectroscopy and DFT calculations is employed. DFT calculations can be used to calculate Raman spectra of the  $\text{VO}_x/\text{CeO}_2$  catalyst to aid the interpretation of the experimental operando Raman results. Since calculated Raman spectra for this system are completely new to literature, the influence of different cell sizes on the resulting spectrum was tested in this project.

## Methods

All calculations in this project were performed using the Vienna ab initio simulation package (VASP) (URL: <http://cms.mpi.univie.ac.at/vasp>). A license for the code is available for the group of Prof. Dr. Christian Hess. Structure optimizations were performed for ceria cells of  $p(2 \times 2)$  and  $p(3 \times 3)$  cell sizes with a  $\text{VO}_3$  cluster deposited on the surface and vibrational frequencies were calculated using density functional perturbation theory (DFPT). Raman intensities were calculated

using a finite difference approach based on the dielectric tensor. A detailed description of the approach is given in reference [3].

## Results

Structural relaxations were performed for ceria p(2x2) and p(3x3) cells with a deposited VO<sub>3</sub> cluster as described above. The structures were relaxed until the residual forces were <0.01 eV/Å. The resulting structures are shown in figure 1.

Normal mode analysis was performed for the structures shown in figure 1 and the Raman intensities were calculated based on the obtained frequencies as described in section 1.5.2. The resulting spectra are shown in figure 2.

## Discussion

Upon deposition of the VO<sub>3</sub> cluster, the electronic structure of the ceria changes. Since the vanadium atom in the isolated VO<sub>3</sub> cluster should have an oxidation state of +VI, but the ceria keeps the vanadium atom of the cluster deposited on the surface always at +V, one electron from oxygen 2p states is transferred to the vanadium atom. [4] It could be shown that the electronic structure change differs for p(2x2) and p(3x3) cells. The electron transferred to then vanadium atom has contributions from three oxygen atoms of the CeO<sub>2</sub> for the p(2x2) cell and four oxygen atoms for the p(3x3) cell. These oxygen atoms are oxidized from -II to (-II+x) with x=0.33 for the p(2x2) and x= 0.25 for the p(3x3) cell. Based on another DFT project in our group (1024) similar structural differences could also be observed for VO and VO<sub>4</sub> clusters. The total energy and the vibrational frequencies of the V-O vibration at ~850 cm<sup>-1</sup> for the p(2x2) cell are in agreement with the literature [5] but the vibrational frequency for the V-O bond also differs between the cell sizes. The peaks are ~25 cm<sup>-1</sup> apart. Furthermore, differences in the Raman spectra of the two different cells are observable. Apart from a shift for the same peaks (V-O at ~850 cm<sup>-1</sup> and V-O-Ce at ~725 cm<sup>-1</sup>) of between 15 cm<sup>-1</sup> and 25 cm<sup>-1</sup>, relative intensities also differ for the two cell sizes. Interphase bonds between 480 cm<sup>-1</sup> and 650 cm<sup>-1</sup> are more intensive for the small cell size and an additional peak can be observed at 675 cm<sup>-1</sup>. This peak is caused by an oscillation of the two V-O-Ce bonds of the two interphase oxygen atoms contributed by the VO<sub>3</sub> cluster, which is only observable for the small cell size.

These findings may indicate, that the p(2x2) cell size is too small to accurately describe the vanadia monomers on the ceria surface. The monomeric species may interact with each other through the periodic boundary conditions. This might indicate that the vanadia loading on p(2x2) cells is too high and, in reality, the vanadia structures would be thermodynamically favoured to form dimeric or oligomeric species. Characteristic ceria vibrations like the F<sub>2g</sub> at 370 cm<sup>-1</sup> and the Ce-O transversal surface phonon between 220 cm<sup>-1</sup> and 300 cm<sup>-1</sup> are also more pronounced for the p(3x3) cell. The broad band of the Ce-O surface phonon is caused by the participation of the VO<sub>3</sub> cluster in multiple vibrations with different frequencies resulting in a

broad region of Ce-O vibrations in comparison to literature results [6]. These results lead to the conclusion, that the p(2x2) cells are approximations, which need less calculation time but the p(3x3) cells are more accurate and are therefore favoured for calculations of Raman spectra.

## Figures

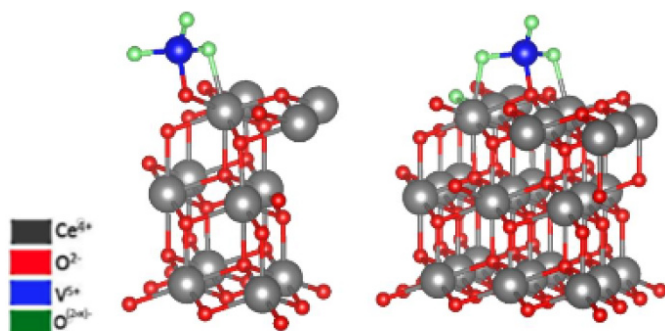


Figure 1: Structures for a  $\text{VO}_3$  cluster deposited on a ceria p(2x2) cell (left) and a p(3x3) cell (right) with  $<0.01$  eV/Å residual forces.

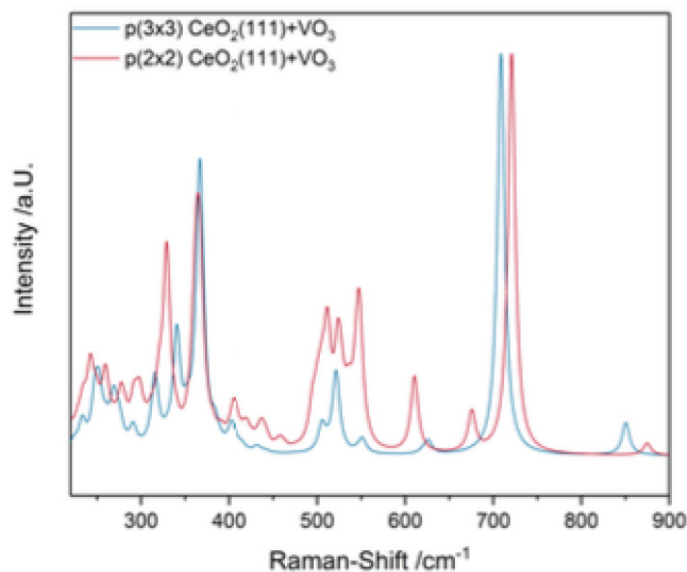


Figure 2: Raman spectra calculated for the ceria p(2x2) and p(3x3) cell as shown in figure 1. The positions of the peaks were calculated using normal mode analysis.

## Publications

Schumacher, Leon. "Oxidative dehydrogenation of propane over ceria supported vanadia catalysts: operando spectroscopy and DFT calculations." (2019). <http://tubama.ulb.tu-darmstadt.de/id/eprint/15900>

## Reference

[1] Carrero, C. A., Schloegl, R., Wachs, I. E., Schomacker, R., ACS Catal., 4, 3357-3380 (2014).

[2] Dinse, A., New Insights into the Oxidative Dehydrogenation of Propane and Ethane on Supported Vanadium Oxide Catalysts, TU Berlin, Berlin (2009). <http://dx.doi.org/10.14279/depositonce-2103>

[3] Schilling, C., Operando Spectroscopy and DFT Modeling of Gold/Ceria Catalysts for CO oxidation and Water-Gas Shift Reactions, TU Darmstadt, Darmstadt (2018). <http://tuprints.ulb.tu-darmstadt.de/id/eprint/7546>

[4] Huang, C., Wang, Z.-Q., Gong, X.-Q., C. J. Catal., 39, 1520-1526 (2018).

[5] Popa, C., Ganduglia-Pirovano, M.V., Sauer, J., J. Phys. Chem. C, 115, 7399-7410 (2011).

[6] Schilling, C., Hofman, A., Hess, C., Ganduglia-Pirovano, M. V., J. Phys. Chem. C, 121, 20834-20849 (2017).

*Last Update:* 2022-06-14 17:45