

# Rational Design of Narrow-Hysteresis Materials by Tailoring Magnetoelastic Interactions II

Project Manager  
Dr. Olga N. Miroshkina

Principal Investigator  
Dr. Markus E. Gruner

Project Term  
2021 - 2022

Clusters  
Lichtenberg II Cluster Darmstadt

Software  
VASP

Additional Software  
Phonopy

Institute  
Center for Nanointegration

University  
Universität Duisburg Essen

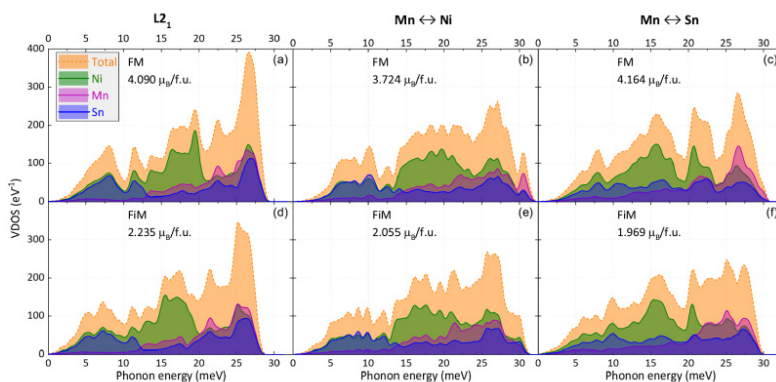


Figure 1: Calculated total and element-resolved VDOS for the ideal  $L2_1$  structure (a), (d) and systems with antisite disorder introduced by swapping of Mn and Ni atoms (b), (e) and Mn and Sn atoms (c), (f). Gaussian smearing with a width of 0.0725 THz is used for better visibility. Results for the ferromagnetic (FM) and ferrimagnetic (FiM) configurations are presented in parts (a)–(c) and (d)–(f), respectively. The magnetic moments of each structure (in  $\mu_B/f.u.$ ) are given in the figures. Copyrighted by APS. Permission for reproduction in technical report has been granted. Published in Phys. Rev. B 106, 214302 (2022).

## Introduction

The current project aims to reveal the relevant intrinsic mechanisms responsible for the coupling of the lattice and magnetic degrees of freedom, providing insight into their contribution to the first-order nature of the magnetic phase transition and hysteresis in state-of-the-art magnetocaloric materials. We carry out the first-principles study of the electronic structure and calculate the total energy, magnetic properties, and electronic and vibrational density of states as a function of the macroscopic state variables (magnetization, volume, and strain). From these data, thermodynamic quantities such as free energy or entropy can be derived, which allow getting information about the contribution of specific elements or particular degrees of freedom. This, in turn, enables us to characterize the free energy barriers with respect to the coupling between electronic, lattice, and magnetic degrees of freedom. In the end, we aim to predict novel highly-efficient multifunctional materials with narrow hysteresis and provide an insight into the intrinsic mechanisms.

## Methods

To describe structural, electronic, magnetic, and vibrational properties of the materials at the nanoscale, we used density functional theory (DFT) as implemented in the Vienna *ab initio* simulation package (VASP). This code is capable of modeling of large systems on super-computer hardware, which is essential for the phonon calculations. VASP uses a plane-wave basis set to describe the wavefunctions of the valence electrons and treats the interaction with the core electrons within the Projector Augmented-Wave (PAW) approach. Exchange-correlation energy was treated in the framework of the semi-local generalized gradient approximation, which depends on the local electron density and its gradients, in the Perdew-Burke-Ernzerhof (PBE) formulation. Phonon calculations were performed in the framework of the direct (force-constant) method. VASP was used for the calculation of Hellmann-Feynman forces, while for postprocessing and the selection of the atomic displacements we used Phonopy.

## Results

During last year, we calculated the energy phase diagram of the Ni-Mn-(Sn,In) Heusler alloys. We compared the energy of ferrimagnetic  $L1_0$ , ferromagnetic  $L2_1$ , and twinning ferrimagnetic structures of  $Ni_8Mn_5In_3$  and  $Ni_8Mn_5Sn_3$ . The most attention, however, was paid to the stoichiometric  $Ni_2MnSn$  Heusler alloy focusing on its magnetic and vibrational properties. We calculated total and partial vibrational densities of state (VDOS) of the ideal  $L2_1$  structure and compared Sn-VDOS with the experimental results of our collaborators. We found a nice agreement in the low-frequency range, while the agreement was less obvious in the high frequencies. To find the reason, we calculated VDOS for structures with two variants of antisite and magnetic disorder. Using results of phonon calculations performed on Lichtenberg HPC, we associate the peaks in the VDOS with particular features in the element-resolved phonon dispersion of  $L2_1$  ordered  $Ni_2MnSn$ .

## Discussion

The good agreement between theory and experiment in the low-energy region provides the evidence that the inversion of optical modes at  $\Gamma$  involving the displacement of Ni and the heavier main group element atoms, which was predicted previously for other Ni-Mn-based Heusler compounds, is also a characteristic property of  $Ni_2MnSn$ . Introducing different types of magnetic and antisite disorder in our calculations results in a distinctive redistribution and broadening of the Sn-VDOS. Mössbauer spectroscopy at low temperatures confirms this suggestion revealing the presence of several inequivalent Sn sites, which indicates the presence of a considerable amount of site-disorder and other defects (such as, e. g., antiphase boundaries) in the sample. The comparison of the site-resolved VDOS obtained with different kinds of site-disorder realized in our modeling shows that the large peaks at high energies are indeed susceptible to changes in the electronic structure of the environment. These

may arise, e. g., from chemical or magnetic disorder or particular modeling of exchange and correlation on the transition metal sites, which explains the remaining differences between the experimental and calculated Sn-VDOS. We showed that the particular deviations between theory and experiment can be discussed in terms of structural and magnetic defects. The good agreement with experimental data documents the predictive power of DFT also for the vibrational properties of Heusler compounds with main group elements from the fourth row.

## Publications

Cugini, F.; Chicco, S.; Orlandi, F.; Allodi, G.; Bonfá, P.; Vezzoni, V.; Miroshkina, O.N.; Gruner, M.E.; Righi, L.; Fabbrici, S.; Albertini, F.; De Renzi, R.; Solzi, M.: "Effective decoupling of ferromagnetic sublattices by frustration in Heusler alloys." Phys. Rev. B 105, 174434 (2022)  
<https://doi.org/10.1103/PhysRevB.105.174434>

Miroshkina, O.N.; Eggert, B.; Lill, J.; Beckmann, B.; Koch, D.; Hu, M. Y.; Lojewski, T.; Rauls, S.; Scheibel, F.; Tauble, A.; Šob, M.; Ollefs, K.; Gutfleisch, O.; Wende, H.; Gruner, M.E.; Friak, M.: "Impact of magnetic and antisite disorder on the vibrational densities of states in Ni<sub>2</sub>MnSn Heusler alloys." Phys. Rev. B 106, 214302 (2022)  
<https://doi.org/10.1103/PhysRevB.106.214302>

Markus E. Gruner, invited talk "A first-principles perspective on the interplay of magnetism and microstructure in Ni-Mn-based Heusler alloys", ICOMAT 2022, virtual, 13 - 18 March, 2022.

Olga N. Miroshkina, status report of B06 subproject of CRC/TRR 270 "Rational design of narrow-hysteresis materials by tailoring magnetoelastic interactions", Summer School of CRC/TRR 270 - Hysteresis design of magnetic materials for efficient energy conversion, Bonn, Germany, 25 - 29 April, 2022.

Markus E. Gruner, invited talk "A first-principles perspective on the interplay of magnetism and microstructure in Ni-Mn-based Heusler alloys", CIMTEC 2022, Perugia, Italy, 20 - 29 June, 2022.

Olga N. Miroshkina, contributed talk "Complex magnetic ordering in Ni-Mn-(In, Sn) Heusler alloys", 12th International Conference on Magnetic and Superconducting Materials (MSM22), Duisburg, Germany, 28 August - 2 September, 2022.

Olga N. Miroshkina, contributed talk "Tuning of the effective magnetic decoupling in Ni-Mn-(In,Sn) Heusler alloys", DPG Meeting of the Condensed Matter Section (SKM), Regensburg, Germany, 4 - 9 September, 2022.

*Last Update:* 2023-10-27 16:23